

Yu. A. Kuznetsov  
E. G. Timoshenko

## Influence of reptations on conformations of a homopolymer in a Monte Carlo simulation

---

Yu. A. Kuznetsov · E. G. Timoshenko (✉)  
Theory and Computation Group  
Department of Chemistry  
University College Dublin  
Belfield, Dublin 4, Ireland  
e-mail: edward.timoshenko@ucd.ie  
Tel.: +353-1-7062821  
Fax: +353-1-7062127

**Abstract** We study the role of topological restrictions for the conformational structure of a nonphantom homopolymer chain in a lattice Monte Carlo model. In the athermal regime we find that the standard Metropolis algorithm violates the detailed balance condition if both local monomer and global reptational moves are included; however, if about one reptation is performed per  $N$  local moves the balance is recovered and we obtain the Flory exponent value close to  $\nu = 0.588$ , where  $N$  is the degree of

polymerisation. We also find that the structure of the collapsed globule is different at equilibrium from that after the late stage of folding. Namely, due to reptations the end and, even more so, the penultimate monomer groups tend to be buried inside the globule core with other monomers, thus being more exposed to the surface.

**Key words** Homopolymer · Simulation · Conformation · Reptation · Nonphantom chain

---

### Introduction

It was recognised early that topological restrictions play an important role in determining the conformation and dynamics of polymer solutions [1]. One of the most important topological restrictions is the integrity of chain links, which implies that different parts of the polymer chain cannot pass through each other. Unfortunately, it is rather difficult to include such restrictions in analytical theories, especially in simple mean-field ones.

Nevertheless, the effects of topological restrictions can be properly studied by computer simulation techniques [2]. One such technique developed by the authors in Ref. [3] is based on a lattice Monte Carlo model. Here, the Monte Carlo updates scheme includes local monomer and reptational chain moves. The former is an attempt to move a randomly chosen monomer to a randomly chosen nearby lattice site. The latter is an attempt to move a randomly chosen end monomer to a randomly chosen lattice site near the other polymer end.

It is important to emphasise that this model does not permit moves that would violate the integrity of links, i.e. the chain is strictly nonphantom. This is ensured automatically due to the particular choice of the connectivity and the excluded-volume parameters.

In this article we study how the probability of performing reptational moves affects the conformations of a single homopolymer chain under good and poor solvent conditions. In particular, we compare the globules obtained by a kinetic process and at true equilibrium. Since the kinetics of polymer collapse proceeds through the formation and growth of locally collapsed clusters along the chain, with their final unification into a single globule, one may expect that after the shape-optimisation stage the homopolymer globule possesses a comparatively simple topological structure [3]. Indeed, a typical coil conformation before the quench possesses a statistically small number of entanglements, or knots, and the folding kinetics adds virtually nothing to that number. Further relaxation of the globule towards the equilibrium requires participation of the chain ends and,

thus, can be viewed as an auto reptational stage. This autoreptation time can be estimated as  $\tau_{\text{rept}} = \tau_0 N^3$  [4], which can yield a time of the order of  $10^3$  s under usual experimental conditions [5].

### The good solvent regime

In this section we shall test the Monte Carlo scheme by determining the value of the swelling exponent,  $\nu$ , [1] in the good solvent regime.

Generally, it seems that to improve the convergence of the system to equilibrium various types of global moves, such as reptations, may be included in addition to local ones. The resulting equilibrium state should not depend on the particular scheme involved. To test this assumption let us study how the probability of performing reptations,  $P_r$ , affects the value of the Flory exponent of the coil. The results are presented in Table 1. One can see that the value of  $\nu$  obtained in the scheme without reptations (at the bottom of the left column) is somewhat higher than even the mean-field prediction,  $\nu = 3/5$ . As we increase  $P_r$ ,  $\nu$  starts to decrease. In the limit when only reptations are performed,  $P_r = 1$ , the swelling exponent value is found to be 0.56. Note that for  $P_r = 1/N$  the measured swelling exponent is remarkably close to the most accurate result obtained from renormalisation group theory,  $\nu \approx 0.588$  [1].

We may conclude, therefore, that the scheme with only reptations involved leads to more compact entangled conformations, resulting in an underestimation of the swelling exponent. On the other hand, the scheme with local monomer moves only favours topologically simple conformations as it is rather improbable to create a knot by local movements. If some knots already exist in the initial conformation, the local monomer

movements would tend to disentangle them. Indeed, one can imagine that simple “shaking” of an entangled boot strap would more likely disentangle it rather than entangle it more. This weak topological effect reduces the number of entanglements, which leads to a larger radius of gyration and to overestimation of the swelling exponent in the scheme with local moves only.

Such strong dependence on  $P_r$  is quite unexpected from the point of view of the standard Monte Carlo paradigm. Of course, the Metropolis check in itself is not sufficient for satisfying the detailed balance condition. One also has to ensure that the phase space of the system is sampled uniformly by attempted Monte Carlo moves [6]. Although, this may be quite simple to ensure for pointlike objects, in our case of a nonphantom chain this is not so. The above observations indicate clearly that the current sampling procedure is not uniform, but biased. The bias is present in both schemes with reptations only and local moves only, but has the opposite effect. We have also seen that if about one reptation is performed per  $N$  Monte Carlo steps the topological effects of entanglements and disentanglements balance each other, making the sampling of the phase space essentially uniform and the correct swelling exponent is produced.

However, we should emphasise that this problem of the improper influence of reptations is only present for the Flory coil and it is irrelevant for the ideal coil. Both schemes with local moves only and reptations only would give  $\nu = 1/2$  for the ideal solution. That is why reptation techniques are extremely popular and well justified for studying melts and concentrated solutions, in which reptations may also be the only physically relevant motions. We should also emphasise that if the chain was phantom we would not have this problem either.

**Table 1** Values of the mean squared radius of gyration,  $R_g^2$ , versus the degree of polymerisation,  $N$ , for different simulation procedures. Here  $Q$  is the number of statistical measurements,  $P_r$  is the probability of making reptations in the scheme, with  $1 - P_r$  being

the probability of making local monomer moves. The exponents  $\nu_1$  and  $\nu_2$  were obtained by a least-squares fit of  $\log R_g$  versus  $\log N$  in the ranges 100–1000 and 500–1000, respectively

$N$	$P_r = 0$	$P_r = 1/N$	$P_r = 0.1$	$P_r = 1$
$Q$	80,000	60,000	40,000	40,000
20	13.14	12.55	12.29	11.50
30	22.21	20.74	19.88	18.44
50	42.16	38.50	35.73	32.63
70	64.89	57.66	52.54	48.45
100	98.17	88.15	77.75	72.54
150	162.2	142.7	122.6	112.9
200	227.2	201.2	169.0	156.8
300	381.2	322.7	261.8	245.9
500	696.5	588.1	460.0	435.9
700	1029	856.1	667.2	637.6
1000	1643	1329	991.5	947.7
$\nu_1$	0.608	0.587	0.551	0.559
$\nu_2$	0.619	0.588	0.554	0.560

Even though the effect discussed for the Flory coil is clearly of topological origin, it only presents a problem for the simulation procedure and has no implications for real polymers.

### Structure of the homopolymer globule

In this section we shall study the structural differences between the two globules of an open homopolymer: one with a relatively simple topological structure corresponding to the late stage of folding and the other with topological entanglements. In practice these simulations were carried out in the following way. Using the lattice Monte Carlo method a large set of homopolymer globules was produced by independent kinetic processes starting from initial coil conformations. Reptational moves were not included during this simulation. To produce a true equilibrium distribution for the globule an additional simulation was applied to the set with the number of reptational moves equal to  $P_r = 1/N$ .

Let us introduce the mean squared distances along the chain,  $D_{mn}$ , and their partially summated combinations,  $D_k$

$$D_{mn} = \langle (\mathbf{X}_m - \mathbf{X}_n)^2 \rangle, \quad D_k \equiv \frac{1}{N-k} \sum_{i=0}^{N-1-k} D_{i+i+k}. \quad (1)$$


$D_k$  versus the normalised chain index,  $\hat{k}$ , for polymers of different degrees of polymerisation is presented in Fig. 1. For very small chain indices  $D_k$  does not depend on  $N$  and on the particular simulation procedure, which reflects local packing of monomers in the dense globule.

Let us consider first the behaviour of this function for globules prepared without reptations. For small values of the chain index the function is almost linear up to some crossover value that scales as  $N^{2/3}$ . Then it saturates to some level, which is proportional to the radius of the globule, thus also scaling as  $N^{2/3}$ . Interestingly enough, for values of the chain index in the vicinity of the chain ends  $D_k$  increases once again. This phenomenon actually reflects the mechanism of the polymer collapse during the late coarsening stage. The globule is usually formed by a final unification of two end clusters and, sometimes, a few middle clusters (see e.g. Figs. 4, 6, 10 in Ref. [3]). Thus, the chain ends possess a somewhat higher probability to appear on opposite sides of the globule than the rest of the monomers. This effect in the mean squared distances is fairly weak as the function experiences an increase of about 10% towards the ends.


In fact, this observation is related to the observation that the chain ends are more exposed to the globule surface and it can be better justified by considering the probability of the  $m$ th monomer in the chain to appear on the surface of the globule,  $P_m^{(\text{surf})}$ . This is presented in the left-hand side of Fig. 2. Thus,  $P_m^{(\text{surf})}$  for the kinetic simulation is nearly constant, except for a few monomers at the very chain ends. In particular, for the end monomer this probability is about 1.3 times larger than that for a monomer in the centre of the chain.

The effect due to applying reptational moves during later kinetic stages is quite distinguishable in Figs. 1 and 2. For sufficiently large values of the chain indices,  $\hat{k} \gtrsim 0.35-0.4$ , the function of the mean squared distances obtained from a simulation with reptations (see lines denoted by diamonds in Fig. 1) lies below the appro-

**Fig. 1** Plot of the partially summated mean squared distances,  $D_{\hat{k}}$ , versus the normalised chain index,  $\hat{k} = k/(N-1)$ , for homopolymer globules of different sizes and different simulation procedures. Pairs of lines correspond to the following values of the degree of polymerisation (from bottom to top):  $N = 50$ ,  $N = 100$  and  $N = 200$ . Lines denoted by *diamonds* and *pluses* in each pair correspond to the simulation procedures with,  $P_r = 1/N$ , and without reptations,  $P_r = 0$ , respectively

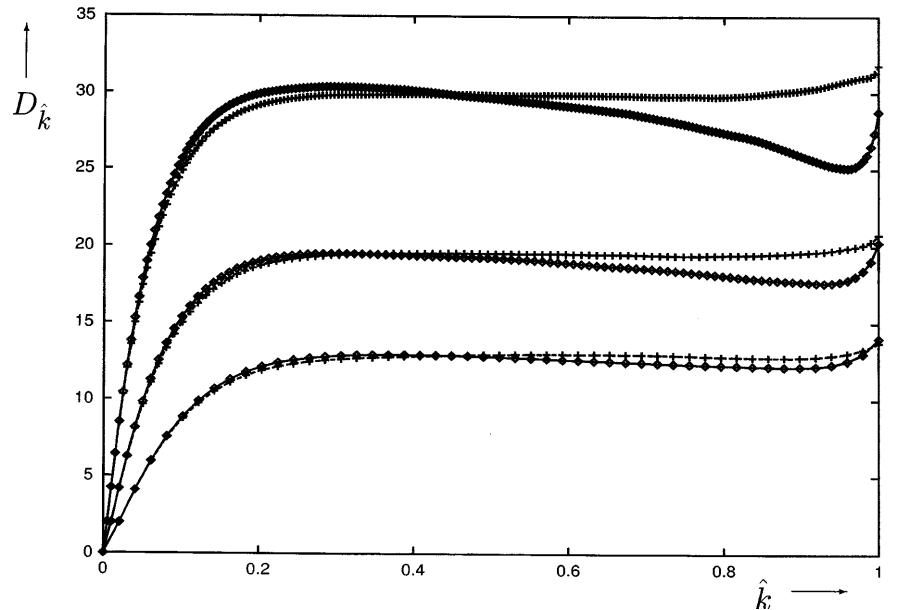

**Fig. 2** Plot of the probability,  $P_m^{(surf)}$ , for the  $m$ th monomer in the chain to appear on the globule surface versus the monomer index,  $m$ , for a homopolymer with a degree of polymerisation  $N = 400$ , for different simulation procedures. The curves on the *left* and on the *right* correspond to the kinetics (no reptations) and reptational simulation procedures, respectively. Both distributions are symmetric in  $m$  and for convenience they are presented only on halves of the interval

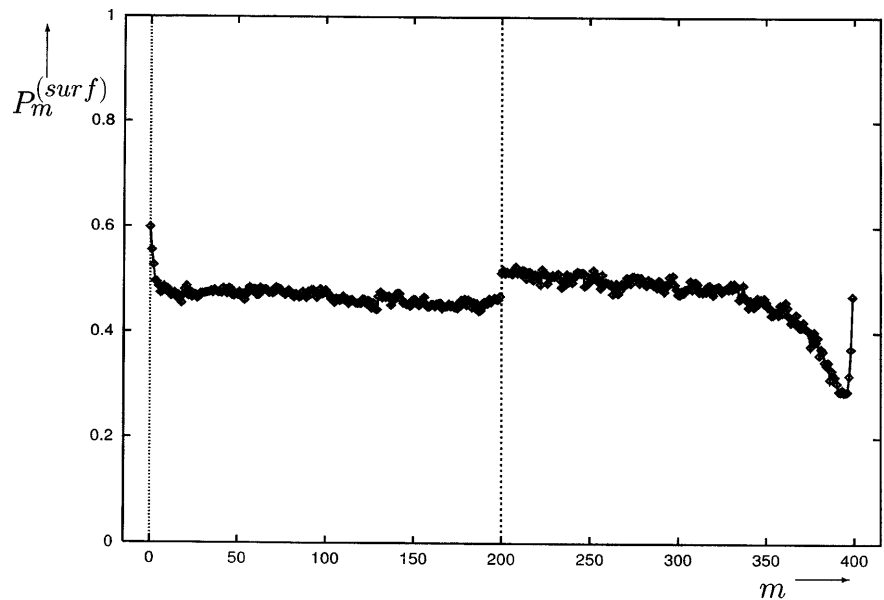

appropriate curves of the kinetic simulation. The situation is just the reverse for smaller  $k$ , with the difference slowly vanishing towards  $k = 0$ . Thus, the reptational curve for  $D_k$  behaves in the following way: it is linear for small  $k$ , reaches a maximum at around  $\hat{k} = 0.3$  and then slowly decreases, reaching a minimum in the vicinity of the chain ends. At the very end the function increases strongly, still being significantly smaller than for  $D_k$  without reptations.

Note that the partially summated mean squared distances are not fully informative due to the role of the end effects in an open chain. Thus, let us consider the mean squared distances as functions of two indices. The ratios of the mean squared distances with and without reptations,  $D_{mn}^{(r)}/D_{mn}^{(n)}$ , are shown in Fig. 3. Depending on the behaviour of this ratio, the monomers in the chain may be roughly divided into three groups: for monomers in the centre of the chain,  $0.1 \lesssim m/N \lesssim 0.9$ , the mean squared distances significantly increase due to reptations; for penultimate groups of monomers in the chain  $3 \lesssim m, N - m - 1 \lesssim 0.1N$ , the distances decrease due to reptations, with the effect becoming more pronounced on approaching the ends of the chain, and for a few end monomers the distances decrease but much more weakly. Thus, we can conclude that reptations push the end groups somewhat and the penultimate groups of monomers more so towards the centre of the globule, thus reducing their mean squared distances between each other and monomers from the central group. As the density of the globule does not change here this leads to an increase in the mean squared distances for monomers in the centre of the chain.


Such behaviour of the mean squared distances is quite consistent with the plot of  $P_m^{(surf)}$  after the

reptational stage (right-hand side of Fig. 2). This quantity increases for monomers in the central group by about 10% and, instead of being constant, decreases slowly towards the ends of the chain. The drop in the probability is most pronounced for monomers from the penultimate groups. The function rapidly increases for a few monomers at the very ends of the chain, although they still possess a lower probability to be found on the surface than monomers from the central group. This rapid increase in the probability for a few end monomers may be interpreted as the effect of a single end seeking to maximise its entropy. Indeed, the chain ends are freest to explore the surface, whilst the rest of the monomers are more restricted due to connectivity.

## Conclusion

In this article we have applied the lattice Monte Carlo model of Ref. [3] to study the role of reptations for conformations of a nonphantom homopolymer chain.

First, we considered the athermal good solvent regime and discovered that the frequency of performing reptations significantly affects the size and even the swelling exponent of the polymer. This problem arises due to a nonuniform sampling of the phase space of the system by attempted Monte Carlo moves when links integrity is strictly insured. For a nonphantom chain it is not clear how to ensure uniform sampling, especially between conformations with different topological numbers. The scheme with reptations only is biased towards entangled conformations, while the scheme with local moves only samples topologically simple states more; however, the balance is recovered when  $P_r = 1/N$ .

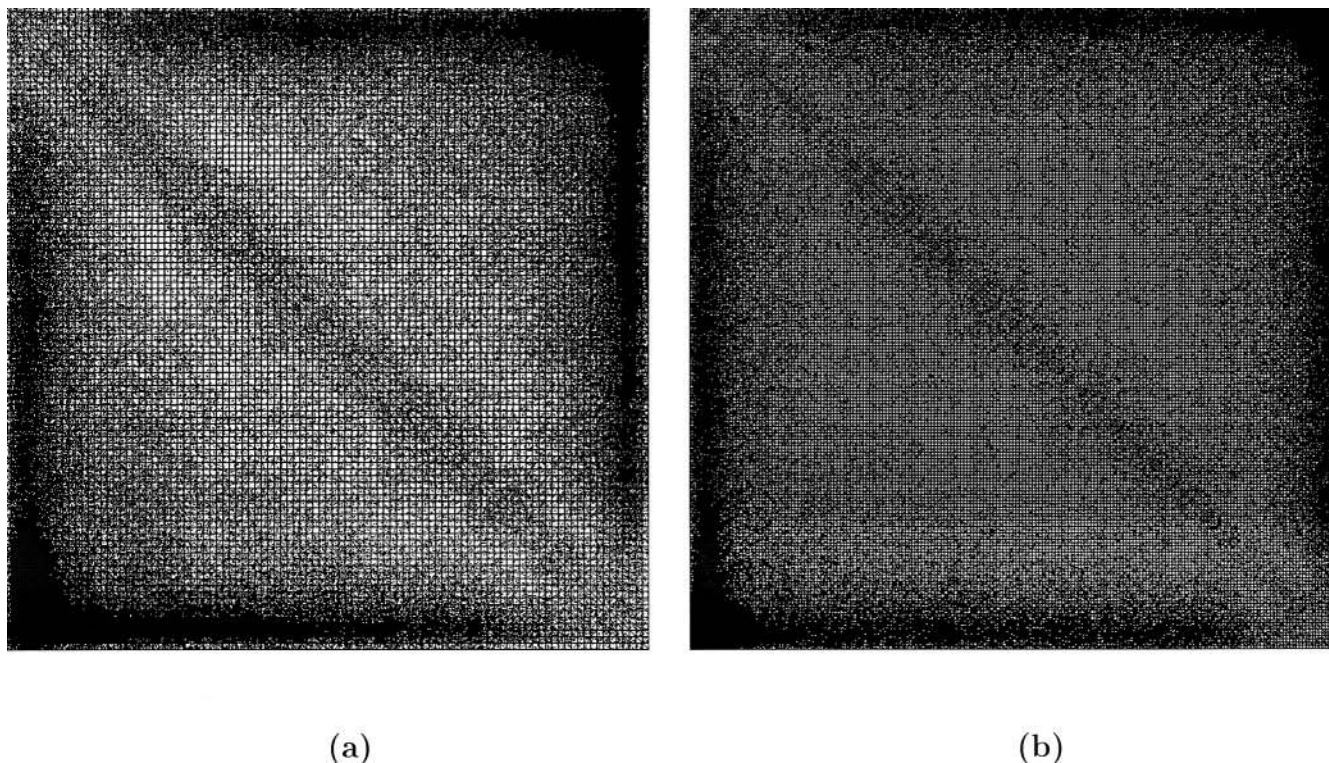

**Fig. 3a, b** Diagrams of the ratios of the mean squared distances with and without reptations,  $D_{mn}^{(r)}/D_{mn}^{(n)}$ , for different values of the degree of polymerisation. **a** and **b** correspond:  $N = 100$  and  $N = 200$ , respectively. Indices  $m, n$  start counting from the *upper left corner*. Each matrix element is denoted by a quadratic cell with a *varying degree of black*; the darkest and the lightest cells correspond to the smallest and to the largest ratios of the mean squared distances, respectively. The intensity of the black colour in the near diagonal elements corresponds approximately to the ratio  $D_{mn}^{(r)}/D_{mn}^{(n)} = 1$

Second, we then compared structures of the two globules: one corresponding to late stages of kinetics and the other to the true equilibrium. The globule after the late kinetic stage is characterised by a uniform monomer distribution except for the end monomers, which have a higher probability to be on the surface. Due to reptations the end and, even more so, the penultimate

monomer groups are pushed more towards the centre of the globule, with the central monomer group thus being more exposed to the surface. A typical magnitude of this effect in observables expressing the  $k$ -dependent properties is about a few dozen percent in the relative change, while the global characteristics, such as the mean energy and radius of gyration, are practically unaffected by this conformational change. The latter is a physically important conclusion for real polymers.

**Acknowledgements** The authors are grateful to K.A. Dawson, F. Ganazzoli, and especially to A.Yu. Grosberg for interesting discussions. We also acknowledge the support of Enterprise Ireland grants SC/99/186 and IC/1999/01 and the support of the Centre for High Performance Computer Applications, University College Dublin.

## References

- (a) de Gennes PG (1988) *Scaling concepts in polymer physics*. Cornell University Press, Ithaca; (b) Doi M, Edwards SF (1989) *The theory of polymer dynamics*. Oxford Science, New York; (c) des Cloizeaux J, Jannink G (1990) *Polymers in solution*. Clarendon Press, Oxford
- (a) Binder K (1984) *Applications of Monte Carlo method in statistical physics*. Springer, Berlin Heidelberg New York; (b) Allen MP, Tildesley DJ (1993) *Computer simulation in chemical physics*. NATO Advanced Study Institute Series C 397. Kluwer, Dordrecht
- Kuznetsov YA, Timoshenko EG, Dawson KA (1995) *J Chem Phys* 103:4807
- Grosberg AY, Khokhlov AR (1994) *Statistical physics of macromolecules*. American Institute of Physics, New York
- Grosberg AY, Kuznetsov DV (1993) *Macromolecules* 26:4249
- (a) Parisi G (1986) *Les houches. Session XLIII*. North-Holland, Amsterdam; (b) Parisi G (1988) *Statistical field theory*. Addison-Wesley, Reading, Mass